

Customer: [REDACTED]

Machine Used: TensileTurn – Industrial Upgrade Model

Date: [REDACTED]

Prepared By: [REDACTED]

Machined Specimens:

- Standard ASTM 0.350" round bar specimen
- Standard ASTM 0.505" round bar specimen
- Non-Standard ASTM 0.505" round bar specimen

Machining Conditions:

All specimens were machined using Hysol MB10 coolant, with cutting parameters tailored to suit the material properties. A tailstock was used to provide additional support during machining. Specimens were pre-center-drilled prior to the turning operations. Due to their square cross-section, all parts were secured using a 4-jaw independent chuck for proper alignment and stability.

Turning Operations:

Operation 1: Roughing and finishing of the outer diameter

- **Tool:** SDJCR, Radius: 0.0157"

Operation 2: Finishing of the outer diameter (right side)

- **Tool:** SDJCL, Radius: 0.0157"

Operation 3: Cut-off operation

Notes:

- Aside from the non-round cross-sectional shape, no major difficulties were encountered during machining.
- The Non-Standard ASTM 0.505" specimen had a long and narrow geometry, making it prone to vibration and chatter, particularly during the finishing stage. To mitigate this, the surface speed was significantly reduced, resulting in a duller (opaque) finish, though dimensional accuracy remained within acceptable limits.
- All specimens were machined under standard testing conditions. Customers performing continuous machining may benefit from optimizing feeds, speeds, and tool selection to improve efficiency and surface quality.
- Machining was performed in alignment with the requirements outlined in ASTM E8.




• 2220 Meridian Blvd., Suite #AF937, Minden, NV, 89423, USA
• 11407 SW Amu St., Tualatin, OR, 97062, USA
• 4071 L.B. Mcleod Rd. Ste D PMB 34, Orlando, FL, 32811, USA
• 847 Sumpter Road, Belleville, MI, 48111, USA
• 918 16 Ave NW, Calgary, AB, T2M 0K3, Canada

+1 (877) 672 2622

775-981-9041

sales@tensilemillcnc.com

www.tensilemillcnc.com

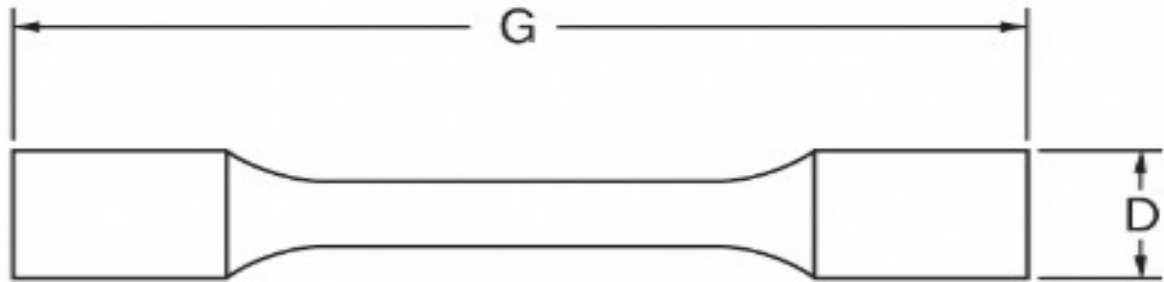

ASTM E8 Schematic Representation

Cutting Conditions – By Specimen:

Standard ASTM 0.350" Round Bar Specimen:

- **Surface Speed (SFM):** 600 feet/minute
- **Feed per Revolution:** 0.004 inches/rev
- **Depth of Cut:** 0.0035 inches per radial pass
- **Cycle Time:** 7 minutes
- **Video Link:** [REDACTED]



Standard ASTM 0.505" Round Bar Specimen:

- **Surface Speed (SFM):** 600 feet/minute
- **Feed per Revolution:** 0.004 inches/rev
- **Depth of Cut:** 0.0035 inches per radial pass
- **Cycle Time:** 7 minutes
- **Video Link:** [REDACTED]





Non-Standard ASTM 0.505" Round Bar Specimen:

- **Surface Speed (SFM):** 600 feet/minute (initial); reduced to 100 feet/minute for finishing
- **Feed per Revolution:** 0.004 inches/rev
- **Depth of Cut:** 0.0035 inches per radial pass
- **Cycle Time:** 20 minutes
- **Video Link:** [REDACTED]

